ASSA ABLOY AUSTRALIA

TEST REPORT # 2012059-2

SnapLock Fixed Security Window Grille (Large Diamond) Sample Number – 145984-10

FOR

Prowler Proof



NATA Accredited Laborator Number: 14426

Accredited for compliance with ISO/IEC 17025

ENG054/6 Report No.2012059-2

Date of issue: 12/09/2012

	Test Report Security Window Grille		
Test Report Number:	2012059-2	Project Number:	10541
Manufactured By:	Prowler Proof	Date of Submission:	09/09/2012
Tested By:	C Horton	Date Tested:	09/09/2012
Certified By:	A Sterrenberg		
Witnessed By:	Michael Henry – Prowler Proof		

Details of Test Window

Type and Class:	Type 1 Class A
Make or Model:	SnapLock - Large Diamond
Sample Number:	145984-10
Frame Size:	1500mm x 900mm
Framing Material:	Pinus Radiata – 70mm x 35mm
Constructional Desc	ription of Test Security Window Grille:
Fixed security window	grille with infill secured utilising Prowler Proof SnapLock method. Frame corners welded.

Details of Test Window Infill

Type and Fabrication Method:	Extruded and expanded aluminium diamond grille.			
Manufacturer's Name / Part Number:	Prowler Proof - PPLD127			
Type 1 Mesh Infill (if applicable)				
1) Number of Intersected Strands in a 1	150mm Circle: 8			
2) Breaking Force in Shear of One Stra	and (min 3kN): 4.93			
3) Multiplication of Above Points 1 and	d 2 (min 30kN): 39.50			

(Above details supplied by customer not by testing authority)

Test Report Security Window Grille

Dynamic Impact Test - AS 5039/5041

Test	Remarks	Pass	Fail
Impact One:	Grille secure in frame.	ü	
Impact Two:	Grille secure in frame.	ü	
Impact Three:	Grille secure in frame.	ü	
Impact Four:	Grille secure in frame.	ü	
Impact Five:	Grille secure in frame.	ü	
150mm Diameter Probe test using R.M.F:	-	ü	
65mm Probe check:	-	ü	

<u>Jemmy Tests - AS 5039/5041</u>

Location	Remarks	Pass	Fail			
Centre Locking Point:						
Bottom Locking Point:						
Top Locking Point:	No man and a sill and for immediate De					
Centre Hinge:	No gap arose to allow for jemmy tests - Pass					
Bottom Hinge						
Top Hinge:						

Infill Pull Tests - AS 5039/5041

Location	A 450mm Maximum	B 150mm Maximum	C 100x100mm Maximum	D	E	Pass	Fail
Centre Grille (1.5kN):	ü	ü	ü	ü	ü	ü	
Top Corner, Lock Side (1.5kN):	ü	ü	ü	ü	ü	ü	
Bottom Corner, Lock Side (1.5kN):	ü	ü	ü	ü	ü	ü	

- A Maximum size of any gap between grille and grille frame or grille frame and door frame under load (dynamic).
- B Maximum size of any gap between grille and grille frame or grille frame and door frame after load (static).
- C The size of any gap caused by the infill breaking away from the security grille framing.
- D Whether the grille remained in a fixed position.
- E Whether the locking device maintained the door in a locked position.

Overall Test	Pass
Remarks:	Impact test - Pass
	Jemmy test - Pass
	Pull test - Pass
	

This signature indicates that testing	has been conducted in accordance to the current AS 5039-2003, and test results reflect the test findings.
The At	Print Name A. Sterrenberg Date 12/09/12
uthorised Signature	Print Name Date (A) Date (A)
	Accredited for compliance with ISO/IEC 17025

Identification Details for Security Window Grille Submitted for Type Testing in Accordance to AS 5039/5041 (Informative)

<u>General</u>

Model Number / Name:	SnapLock LD
Sample Number:	145984-10
Manufactured By:	Gershwin Pty Ltd trading as Prowler Proof
Date of Submission:	11/09/12
Description:	Fixed security screen window
(To show additional specific	DRAWINGS: COMPLETE ATTACHED SHEETS c details of door construction such as internal stiffening, hinging, etc., attach further sheets as necessary)

Framing Section

Туре:	Extruded aluminium				
Manufacturer	's-	Name:	Prowler Proof	Section Number:	SLW11
Attached Dim	ensional Drawing-	Number:	-	Issue:	-
Material Type and Grade:		Aluminium	6060-T5		
Surface Finis	h:	Powder coa	ated		
Mass per Met	re Length (kg):	-			
Mounting Fra	ame Material:	See attach	ed CAD drawings		
		(A	attach drawings if necessary)		

Corner Stake - NA Welded Corners

<u>Infill</u>


Type and Fabrication Mo	ethod:	Large Diamond Grille										
Manufacturer's-		Name	: Prowle	Proof			Part Number:		ber:	PPLD127	PPLD127	
Attached Dimensional D	rawing-	Number	r: -					Is	sue:	-		
Material Type and Grade	e :	Aluminiur	m 6063-T5									
Surface Finish:		Anodised	I									
Diameter of Type 3 Infill	:	See attac	ched									
Means of Securing:		Weld		Scre	W		Riv	et		Other	ü	
	(If mean	s of securin	g is OTHER	submit	full details o	n a s	separ	ate sheet)				
Fastener Details:												
Type: Clamp and bond	Type: Clamp and bonded – Every contact point Part Number: SL Clamp											
Material	Alum	(St.Steel		Monel			Steel		OTHER	ü	
Number Used and Location: See attached – Clamp and bond – Full perimeter												
		(Attach drawings if necessary)										


Manufactured By: Prowler Proof


Sample Number: 145984-10

Location of Fixing Points, Locking Points, Hinges and Mid-Rail – Refer attached CAD drawing SSLD - Testing Sample **Means of Securing Infill to Framing, Location of Welds / Fasteners -** Refer attached CAD drawing SSLD – Snaplock Large Diamond Window

End

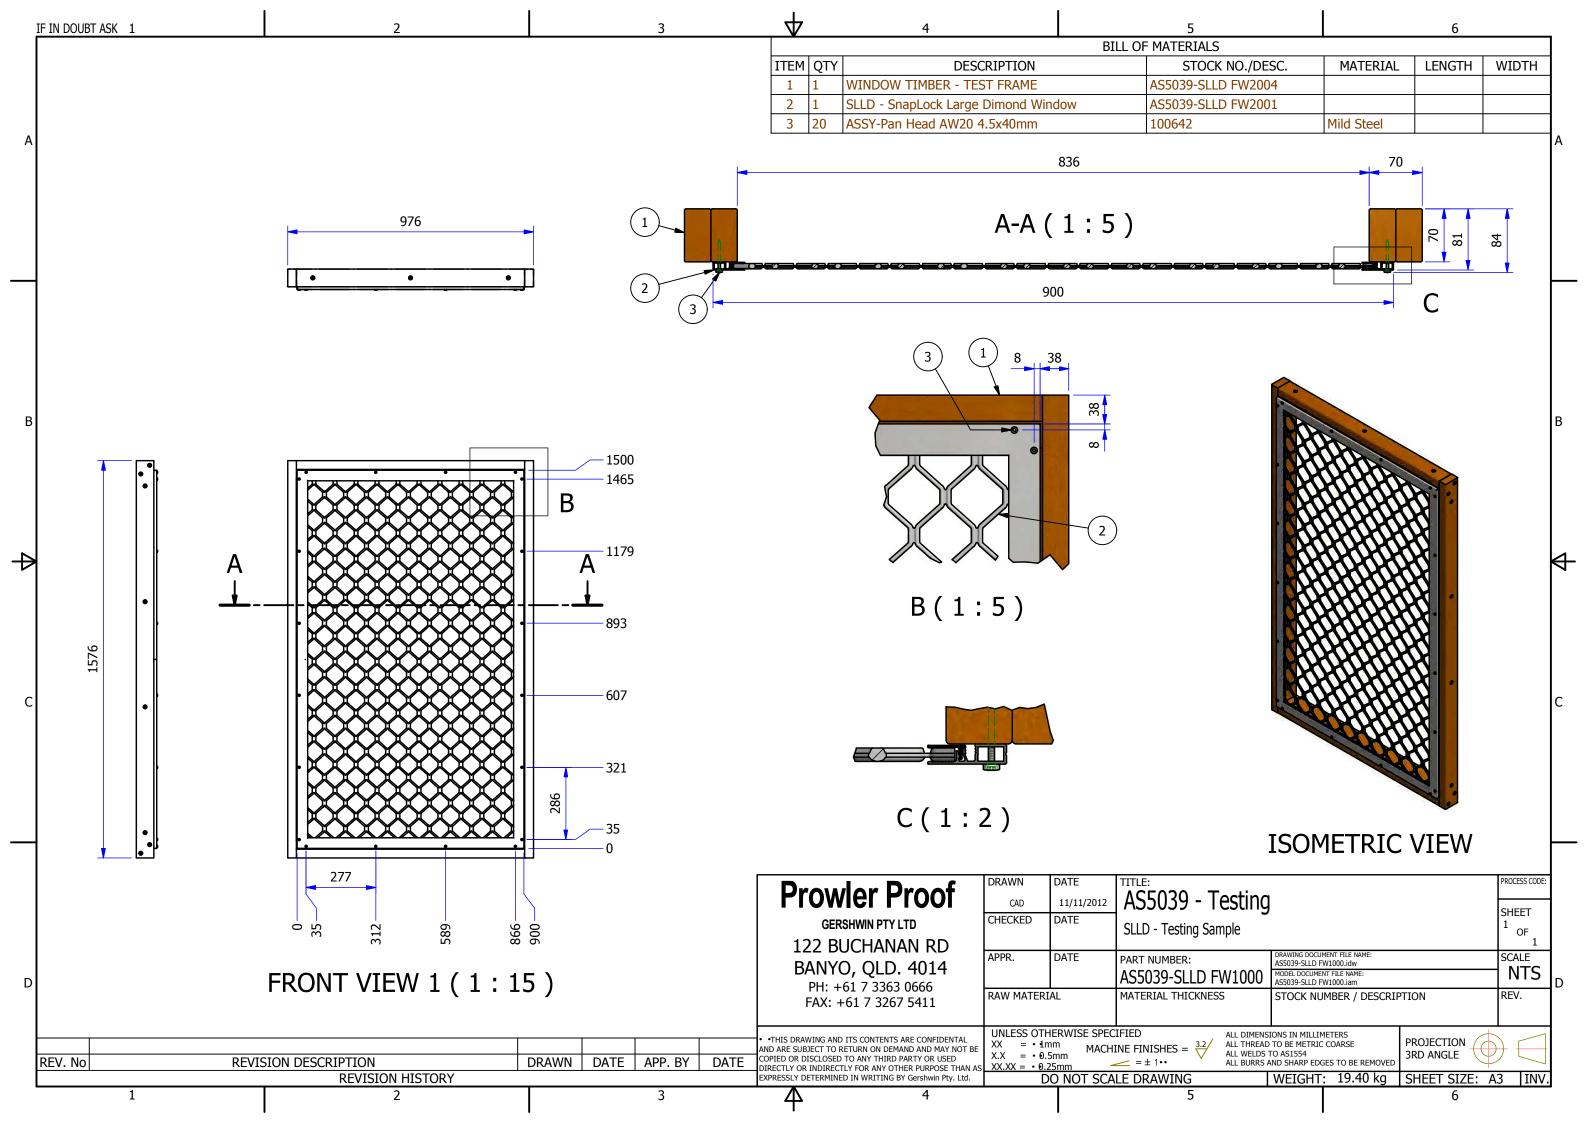

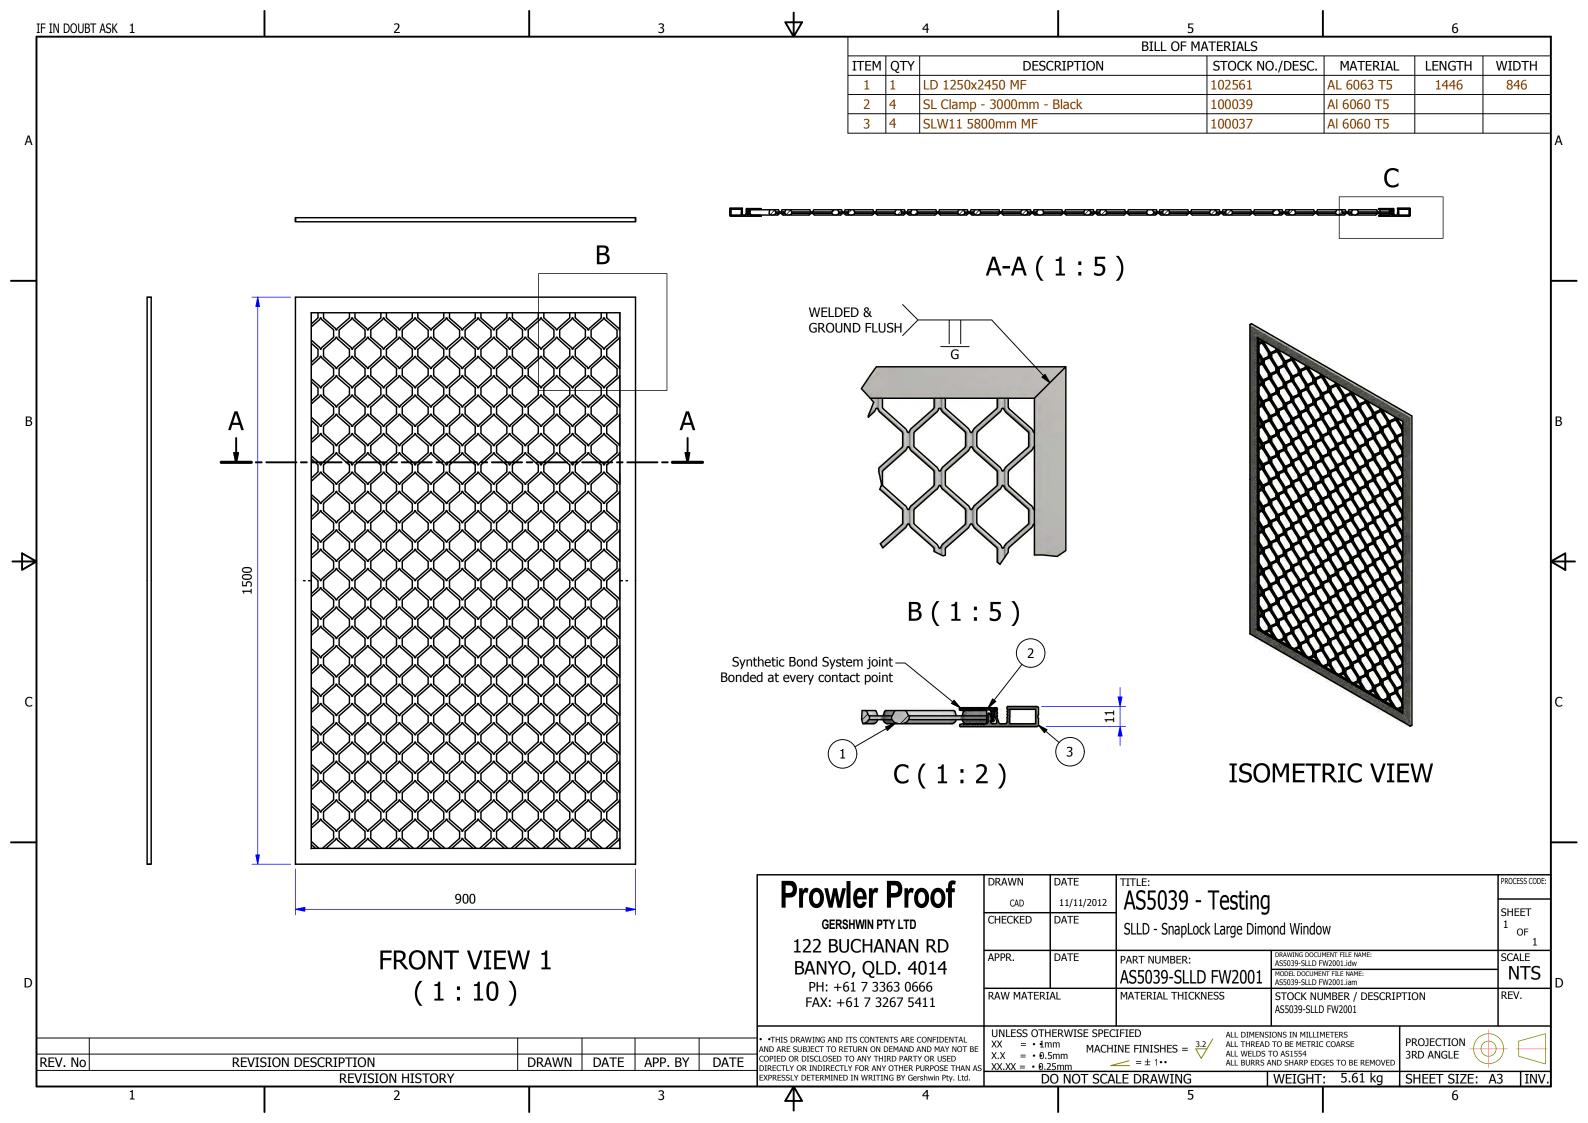

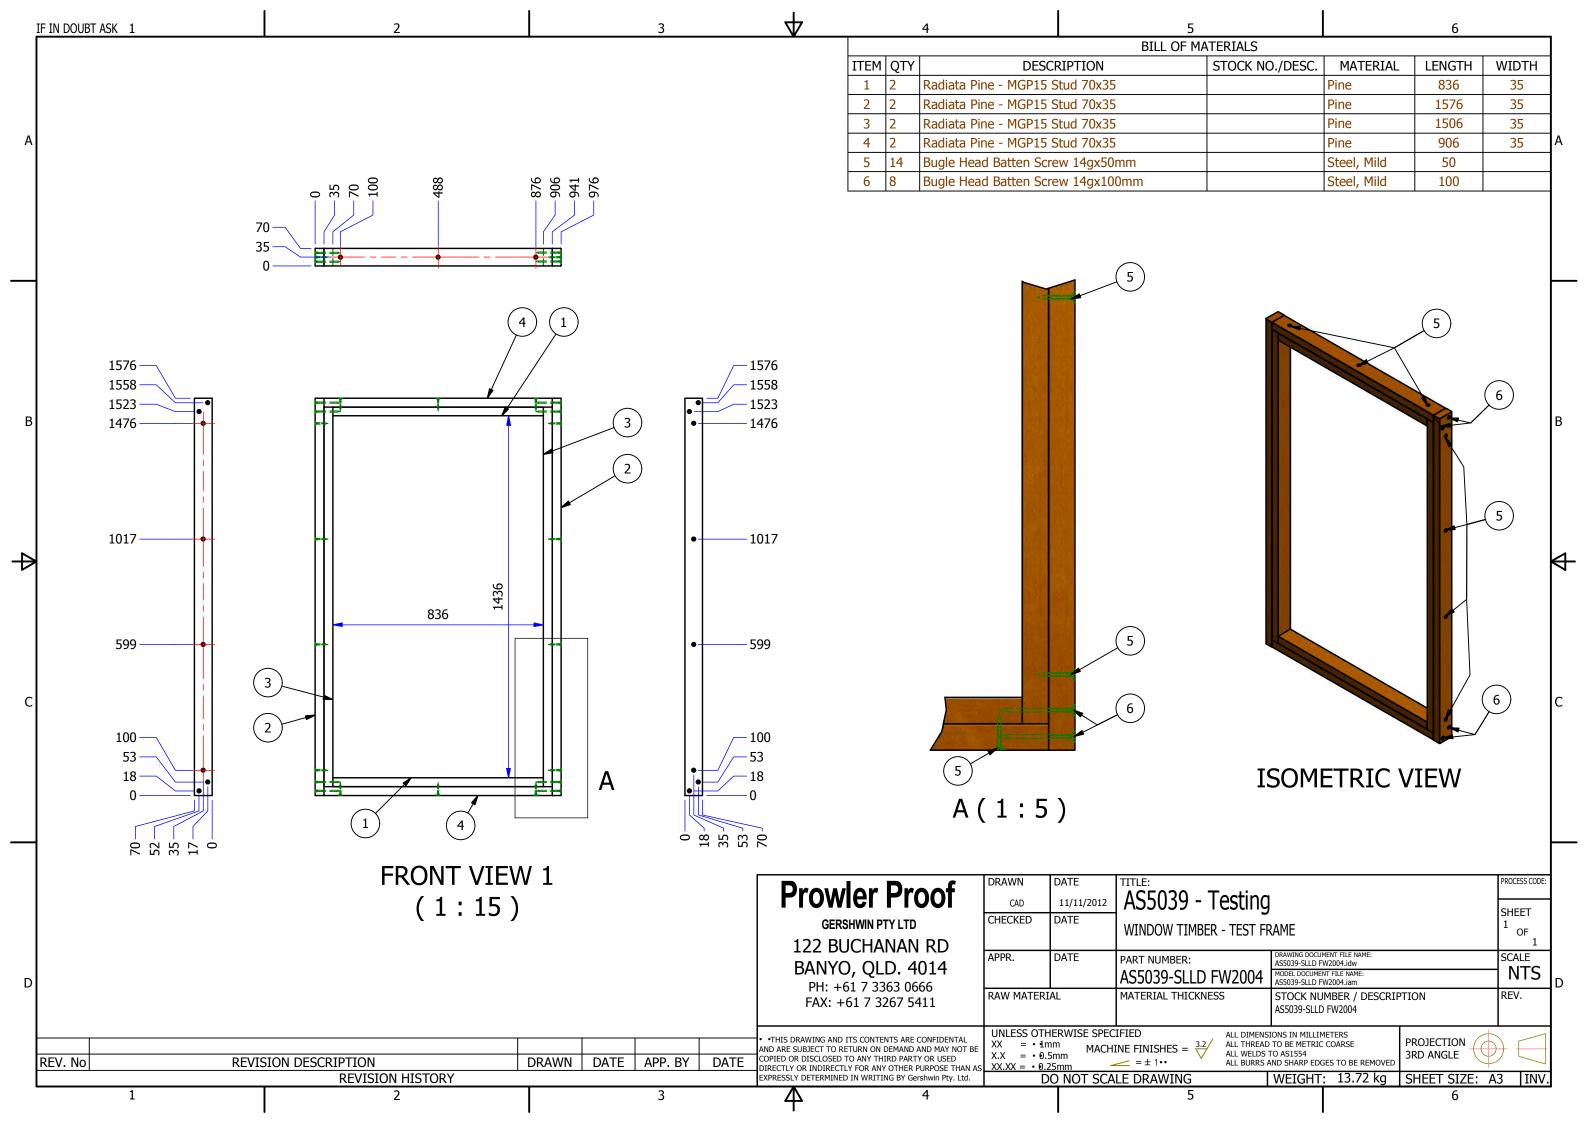







AS5039

TEST REPORT (Shear test only)

Azuma Design Pty Ltd

Address: 160 Newton Rd Wetherill Park NSW 2164 Australia PH: 61(02)9604 0255 FAX: 61(02)9604 0466





SHEAR TEST REPORT

AZT Number:	AZT0064.12	
Date:	1 st May 2012	
Manufactured By: _	PROWLER PROOF	
Sample identification	n: KAU 1865, Alloy Temper 6063	
Surface finish:	Mill finish	Aperture: 60mm
Type: I		

Aim: To test the sample in accordance with Section 7 of AS5041-2003-Methods of test- Security Screen Doors and Window Grilles.

Method:

- Transpose a circle of 150 mm diameter onto the infill of the test specimen. Count and record the number of chords/strands of the infill material/grille that are intersected by the circle.
- Choose a sample chord from the test specimen. For infill material of a regular, uniform design, the sample shall be a typical strand, clear of any knuckles or webs. For infill materials of irregular design and varying strand size, the thinnest structural strand intersected by the 150 mm circle shall be taken.
- Position the sample in the shear apparatus so that its orientation in relation to the cutting edges corresponds approximately to the direction of attack within a cutting tool in situ in an infill.
- Apply a load to the test sample at a rate of 19 mm/min cross-head travel and increase the load until fracture occurs.
- Record the shear force at fracture. If a double shear tool is used, the shear force recorded shall be half that which was measured.

Requirements:

- (a) The breaking force of the chords shall be not less than 30 kN.
- (b) The shear force of any chord shall be not less than 3 kN.

Test equipment:

Azuma Hydraulic test rig Double shear tool

Azuma Design Pty Ltd

Address: 160 Newton Rd Wetherill Park NSW 2164 Australia PH: 61(02)9604 0255 FAX: 61(02)9604 0466

AS5039 Shear Test Report/Issued Date 24-03-05/Revised Date 10.5.10

Page 2 of 4





SHEAR TEST REPORT

Results;

Sample A

Shear	Orientation	Double shear force	Shear force (Half of double shear force)
1	Vertical	9590	4795
2	Vertical	9550	4775
3	Vertical	9330	4665
4	Horizontal	9530	4765
5	Horizontal	10350	5175
6	Horizontal	10190	5095
7	Diagonal	10060	5030
8	Diagonal	10030	5015
9	Diagonal	10260	5130
		Average =	4938.33 N

Î	Number of Intersections of Strands by 150mm Dia Circle: _	8
2	Average Breaking Force in Shear of one Strand (min 3kN):	4.93 kN
	Multiplication of above points 1 and 2 (min 30kN):	39.50 kN
Remarks:	PASSED	

Azuma Design Pty Ltd

Address: 160 Newton Rd Wetherill Park NSW 2164 Australia PH: 61(02)9604 0255 FAX: 61(02)9604 0466





SHEAR TEST REPORT

Shear	Orientation	Double shear force	Shear force (Half of double shear force)
1	Vertical	9980	4990
2	Vertical	9470	4735
3	Vertical	10210	5105
4	Horizontal	10890	5445
5	Horizontal	10320	5160
6	Horizontal	10280	5140
7	Diagonal	10360	5180
8	Diagonal	10230	5115
9	Diagonal	10390	5195
		Average =	5118 N

3	Number of Intersections of Strands by 150mm Dia Circle: _	8	
4	Average Breaking Force in Shear of one Strand (min 3kN):	5.11 kN	
	Multiplication of above points 1 and 2 (min 30kN):	40.94 kN	
Remarks:	PASSED		

CONCLUSION

From the results achieved it is evident that the sample satisfies requirement 7.6 of AS5039-2008-Security screen doors and window grilles.

SIGNATORY NAME	Rob Irwin
SIGNATURE:	
DATE:	1st May 2012

Azuma Design Pty Ltd

Address: 160 Newton Rd Wetherill Park NSW 2164 Australia PH: 61(02)9604 0255 FAX: 61(02)9604 0466

AS5039 Shear Test Report/Issued Date 24-03-05/Revised Date 10.5.10





DATE:	Ist May 2012	
DATE.	I May 2012	

EQUIPMENTS USED TO PERFORM THE ABOVE TEST

EQUIPMENT NAME	EQUIPMENT NUMBER	√ IF USED
Tape Measure	AZTAPE0001	
1500mm Steel Rule	AZRULE0001	
Shear Test Apparatus	AZTEST0009	
Hydraulic Load Test Rig Readout	AZTEST0008	
200 mm Digital Caliper	AZCAL10010	
Knife Shear Knife	AZKNIF0001	
Knife Shear Blade	AZBLAD0001	

Azuma Design Pty Ltd

Address: 160 Newton Rd Wetherill Park NSW 2164 Australia PH: 61(02)9604 0255 FAX: 61(02)9604 0466